

Graphene-based polymer composite membranes for water purification: An Investigation

Aida Mohammadi

Faculty of Engineering, Chemical Engineering Department, Queen's University, Canada

Abstract

At present, a significant progress has been achieved in the field of water filtration and in the global need for low CO₂ producing energy sources, in this regard, membrane technology has played a crucial role. Membrane technology is a rapidly growing research area with several real times applications such as gas and aqueous purification. Notably, there are already some well-established membranes for these applications, however, their accuracy, ability, and cost effectiveness vary depending on membranes' type. Among various membranes, the two-dimensional structure and tunable physicochemical properties of graphene-based materials such as graphene oxide, reduced graphene oxide, and combined with polymers offer an exciting opportunity. This paper presents a brief review of carbon-based membranes for water filtration application. The focus is on the design and fabrication of the membranes, membranes preparation condition, and membranes' physicochemical properties on separation performances. The key issues and challenges for graphene-based membranes are also identified and discussed along with recommendations for future research directions. Addressing these issues will significantly enhance the design and fabrication of these membranes and pave the way for translating them into practical applications.

Keywords: Membrane, Filtration, Two-dimensional Materials, Graphene oxide, Reduced Graphene Oxide.

1. Introduction

Water treatment in gas and aqueous phases with membrane separation has attracted great attention. Reasons include growing water-use from population shifts and complex land-use patterns that require abundant water and heavier request from industry and energy production. Considering the need for water purification, technologies that can efficiently separate ions and molecules of water are highly desirable. In particular, these technologies aim to develop such water-based membranes for maximum separation efficiency and exceptional permeance. Ideally, an efficient membrane should be able to maximize the water permeance, to be robust enough to

resist the applied filtration pressure, and to have a narrow distribution of pore size for excellent selective separation. Owing to the excellent mechanical property, chemical stability, and availability of rich functional groups, graphene-based materials such as graphene oxide (GO) and reduced graphene oxide (rGO) are widely being researched for membrane application. To this end, numerous efforts have been made to fabricate graphene-based membranes, and particularly combined with polymers as composite membranes for filtration application.

The filtration concept utilizes polymeric and graphene-based membranes for separation of ions and molecules from aqueous solutions. Polymeric nanofiltration membranes are emerged as a promising method for filtration on the laboratory scale [J. H. Hanemaaijer *et al.*, *Journal of Membrane Science*, 1989, 40, 199–217]. Although polymeric membranes are widely used due to their low cost, they have limitations including less resistance to high temperature and chemicals, and membrane fouling [G. M. Geise *et al.*, *Polymer Science Part B: Polymer Physics*, 2010, 48, 1685–1718]. The limitations associated with the use of polymeric membranes can be possibly overcome with the use of graphene-based membranes.

This study aims to investigate recent developments with respect to the design and fabrication of graphene-based membranes for water filtration application. In this regard, membrane synthesis methods, membranes preparation condition, membranes' physicochemical properties on separation performances are discussed. Finally, the current limitations of graphene-based and future directions for their development are discussed.

2. Graphene oxide (GO) membranes

A perfect molecular level separating unit for any kind of species to be filtered is on very high demand. In recent years, GO has emerged as an important material which can filter ions and molecules as a membrane. A membrane is considered as a barrier with an ability to allow the passage of certain species while blocks other depending on characteristics of the membrane and species to be filtered. GO—partially oxidized and stacked sheets of graphene—is a type of two-dimensional nanomaterial with a single-atom thickness. GO sheets include pristine regions, oxidized regions, and a small portion of holes [D. An *et al.*, *Industrial and Engineering Chemistry Research*, 2016, 55, 4803–4810].

Due to a large number of surface functional groups, GO sheets can be stacked on top of each other to form a uniform laminar structure with a well-defined interlayer space [J. Y. Chong *et al.*, *Journal of Membrane Science*, 2018, 549, 385-392]. Tunable interlayer spaces within lamellar GO membranes offer a more straightforward approach which controls ions and molecules passage and show a potential in separation applications. The unique physicochemical properties of GO notably its exceptionally high surface area and mechanical strength can lead to improved technologies which addressing global environmental challenges. The use of GO in membrane applications is particularly attractive because they are easy to fabricate, mechanically and chemically robust, and can be amenable to industrial-scale production.

The whole structure of GO includes two parts in terms of functionality and participation in reactions: the sp^3 functional oxidized regions and the sp^2 pristine (graphitic) regions (**Figure 1**) [W. S. Hung *et al.*, *Carbon*, 2014, 68, 670-677]. High resolution TEM imaging also reveals other features such as nano-sized holes and small atomic defects in layers of GO [J. H. Hanemaaijer *et al.*, *Journal of Membrane Science*, 1989, 40, 199–217]. The oxidized graphene sheets, GO, acquire multiple defects and the degree of the defects is subject to the additive amount of oxidant and the oxidizing time. The high defect density introduced in the carbon structure significantly lowers the electronic and mechanical properties of graphene. The oxygen functionalities make GO a hydrophilic material which forms stable suspensions in aqueous media.

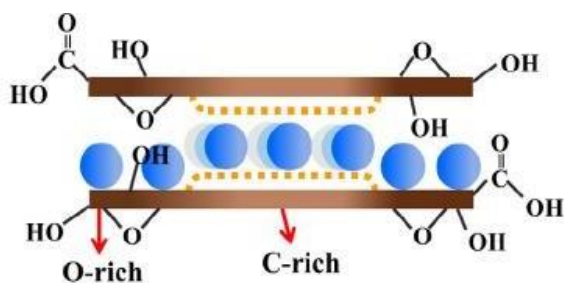


Figure 1. The GO sheets illustrating the hydrophilic O-rich edge, to which H₂O molecules are adsorbed, and the hydrophobic C-rich central region, where there is a low-friction channel (dashed lines) of monolayer H₂O molecules.

The structure of membrane contains a number of GO sheets with lateral size “L”. The functionalized regions act as spacers that keep adjacent GO sheets apart and also prevent them from being dissolved. The pristine regions provide a network of nano-capillaries (commonly termed as “d spacing”) between the GO sheets to provide passage for molecules and ions to diffuse in the direction parallel with the GO sheets (**Figure 2**) [Yue-Heng Xi *et al.*, *Applied Materials and Interfaces*, 2016, 8, 15557-15566]. This d spacing is defined as the center to center distance between two adjacent GO sheets and allows nearly frictionless flow of water molecule layers.

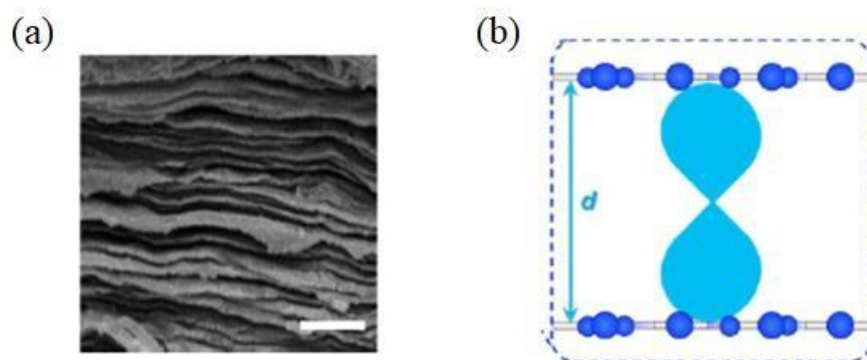


Figure 2. (a) Electron micrograph of the GO film’s cross-section and (b) Schematic view for possible permeation through the GO laminates with lateral size and interlayer space “d”.

GO membranes consist of many stacked layers of GO with an interlamellar spacing of 0.6 - 1.1nm depending on, amongst other things, the degree of hydration. The d spacing between the GO sheets under various relative humidity environments was measured by Liu *et al.* using XRD [R. Liu *et al.*, *T. Scientific Reports* | 7: 9761 | DOI:10.1038/s41598-017-09777-y]. Exposing the GO membranes to water vapor results in a shift in the (001) reflection, which corresponds to an increase in the d spacing. The d spacing was calculated by Bragg’s law: $\lambda = 2d \sin(\theta)$ where λ is the wavelength of the X-ray beam (0.154 nm), d is the distance between the adjacent GO sheets, and θ is the diffraction angle of (001) peak. Because of the existence of oxygen-containing functional groups on GO sheets, the d spacing of the GO membrane composed of stacked sheets is $\sim 6-7 \text{ \AA}$ under dry conditions, which is larger than the d spacing of graphite of $3.4 \text{ \AA}$. As the humidity increases, more water molecules diffuse into the interlayer between GO sheets and d spacing increases accordingly. Therefore, to achieve full potential of GO membranes for high separation performances, d-spacing must be accurately characterized.

The microstructures of GO membranes such as stacking of GO sheets is another important variable affecting GO membranes' compaction. Assembly plays a critical role in the structure-properties relationship of the GO membranes, which in turn controls membranes' separation performances. The membrane microstructure is shown to be affected by membranes preparation methods. GO membranes can be easily fabricated via different methods such as filtration-assisted method, casting/coating, and layer-by-layer (LbL) assembly method. The resulting GO laminates possess excellent mechanical strength due to the strong interlayer hydrogen bonds between adjacent GO layers that hold all the flakes tightly. Compared with filtration-assisted methods, fabricating membranes from the latter is technically challenging and have several disadvantages as described in **Table 1**. The proposed disadvantages severely restrict their promising applications in the GO membranes fabrication [J. Ma et al., *Membranes*, 2017, 7, 52, doi:10.3390/membranes7030052].

Table 1. GO membranes preparation methods.

Method	Description	Disadvantage
Casting/coating based	Drop-casting	Nonuniform deposition of GO nanosheets and poor control over the membrane thickness
	Dip-coating	
	Spray-coating	
LbL assembly	Layer by layer assembly	Not easily scaled-up or energy efficient

In contrast, filtration-assisted methods allow reasonable and easy control over the membrane thickness and microstructure, changed by adjusting concentration and volume of the GO dispersion. Vacuum filtration-assisted method is where aqueous-dispersed GO strongly interacts with a hydrophilic and most commonly used porous media, namely anodized aluminum oxide (AAO) filter paper [C. N. Yeh et al., *Nature Chemistry* 2015, 7, 166-170]. This method results in the formation of a semi-ordered arrangement of the GO layers. In this method, an aqueous dispersed GO strongly interacts with AAO filter discs and strong interaction between hydroxyl and carboxyl groups of GO and AAO filter disc results in the formation of GO membranes with improved mechanical strength. Therefore, vacuum filtration is a potential route for large-scale preparation of the GO membranes, which produces highly stable GO-like lamellar films in water.

Different possible separation mechanism of GO membranes for nanofiltration have been illustrated by literature. Taking the aqueous phase and vapor phase separations as examples, three possible separation mechanisms have been identified within GO membranes [Y. Zhang *et al.*, *Current Opinion in Chemical Engineering* 2017, 16, 9–15]. The selectivity can be achieved by the following mechanisms: size exclusion from the interlayer space of the GO membrane, electrostatic interaction between different ions and negatively charged GO sheets and ion adsorption through the diverse interactions of ions with different regions on GO sheets. Because of size exclusion from the d spacing within the GO membrane, molecules and ions can be separated according to their hydrated radius. The effective volume occupied by an ion in water is characterized by its hydrated radius. In addition to the hydrated radius of ions, both ion charges and its interaction with GO sheets affect the separation performance of the GO membrane. Different anions and cations exhibit different permeation properties through the GO membrane. Carboxyl and hydroxyl groups on GO sheets are ionized in water, which makes the GO sheets negatively charged. This affects the mobility of ions with different electric charges. Finally, separation is achieved by ion adsorption including cation- π interaction and metal coordination to GO sheets. This mechanism indicates that transition metallic cations prefer to interact with the sp^3 C–O matrix via coordination interactions, whereas alkali and alkaline-earth cations prefer to interact with the sp^2 clusters within the GO sheets via cation- π interactions.

The preparation process of the GO membrane can influence greatly the separation performance. The separation performance of GO membranes can be adjusted by changing thickness, lateral sheet size, and degree of oxidation. Two types of pores inside GO membranes can control ionic and molecular transport and the type of which critically depends on the membranes' thickness. Membrane thickness is controlled by changing the concentration and volume of the GO dispersion used for its preparation. Ions and molecules transport pathways in the relatively thin membranes are mainly through pores created by vacancies, holes, and voids formed within individual GO sheets. Also, interconnected interlayer spaces as slit pores formed by stacked GO sheet is dominant only in thick membranes [M. Coleman *et al.*, *Nano Research* 2015, 8, 1128–1138].

The lateral dimensions of GO sheets play an important part in controlling microstructures and properties of GO membranes. Either large or small GO sheets have their merits. Usually, the larger the GO sheet sizes, the higher its C/O ratio [J. Zhao *et al.*, *ACS Nano* 2010, 4, 5245-5252], *i.e.*, smaller GO sheets have more oxygenated groups per unit surface area. In fact, the edge-to-area ratio of a GO sheet increases with the decrease of its lateral dimension. However, a larger sheet brings fewer oxygenated groups per unit surface area. Under this condition, larger sheets can absorb less water through hydrogen bonding and lead to a smaller d spacing and improved mechanical properties. The membranes prepared by smaller lateral sizes have shown more and shorter water transport pathways as compared to those prepared with larger GO sheets. The reason is that more gaps exist between the edges of neighboring smaller GO sheets within the membrane. A larger number of gaps provide more passages for molecules and ions diffusing through the membrane in vertical direction to GO sheets. Therefore, this property (lateral sheet size) is useful for building different GO membranes to either maximize the flux through using small sheets or achieve better separation selectivity by means of larger sheets.

The effect of the removal of oxygen functional groups from GO, which influences separation performance of the GO membranes, will be discussed in the next section.

3. Reduced graphene oxide (rGO) membranes

It is important to determine the effect of GO membrane conditions on filtration capability. One of the target characteristics of the membrane that can be modified includes degree of oxidation. How to effectively remove epoxy and hydroxyl groups is the key for the reduction of GO membranes. The reduction can make a great change in the microstructure and properties of GO by removing oxygen functional groups, thus reducing the d spacing between GO sheets and increasing the barrier properties of the membrane.

Two different approaches are reported to produce rGO membranes: the direct production of electrically conducting rGO membranes and the post-reduction of prefabricated GO membranes. Direct fabrication of rGO membranes as explained by Li *et al.* [D. Li *et al.*, *Nature Nanotechnology* 2008, 3, 101–105] involves the chemical reduction of individual GO sheets in an aqueous dispersion by means of a reducing agent. The procedure is then followed by flow-directed vacuum filtration

of the prepared rGO dispersion. The post-reduction processes applied to parent GO membranes are based on chemical, combined chemical–thermal, or pure thermal processes [O. C. Compton *et al.*, *Advanced Materials*, 2010, 22, 892–896]. Reduction by chemical reagents is based on their chemical reactions with GO. There are two different ways for post-reduction of prefabricated GO papers by chemical processes to produce rGO membranes:

- Aqueous phase post-reduction: prefabricated GO membranes are reduced by immersion in an aqueous solution of a reducing agent at specific temperatures and reduction times.
- Vapor phase post reduction: prefabricated GO membranes are directly exposed to the vapor of the reducing agent at specific temperatures and reduction times.

Among these methods, the solution-based chemical reduction of GO has advantages such as low cost and large-scale production. However, the low solubilities of the chemically rGO sheets lead to the formation of agglomerates in water and most organic solvents due to the strong π - π interactions. In chemical reduction by vapor, rGO membranes with layered structures exhibit better stability in water as they can retain the compact interlayer spacing due to the significantly reduced amount of oxygen functional groups. The enhancement of mechanical properties is attributed to the better ordering of rGO stacks and it leads to water stable rGO membranes [I. K. Moon *et al.*, *Nature Communications* 2010, 1, 1–6]. Thus, the degree of deoxygenation (i.e., reduction) strongly affects the average d spacing of rGO membranes.

After reduction, the C/O ratio is remarkably increased due to the removal of oxygen functional groups. The tightened rGO nanochannels and hydrophobic surface of rGO laminates would be obstructive factors against water transport and improves selective separation. Moreover, upon reduction from GO to rGO, thermal, conductive, and mechanical properties of the membranes are improved. As a result, reduction develops strategies to precisely control nanochannel size within subnanometer scale and concurrently renders water permeation reduction while tuning ions or gases selectivity.

A comparison between thermal reduction and chemical reduction methods are presented in **Table 2**. According to the table, chemical reduction method, particularly vapor phase outweighs the thermal reduction method for rGO membrane production.

Table 2. A comparison between thermal and chemical reduction methods.

Method	Advantages	Disadvantage
Thermal	Better ordering of rGO sheets and reducing d spacing at lower temperature (100°C).	Higher thermal temperature can produce small size and wrinkled graphene sheets/destroy the structure of carbon plane by producing defect.
Chemical	Reduction can be realized at room temperature or by moderate heating/an efficient reduction method/maintain the structure of carbon plan.	Agglomeration of rGO sheets in the aqueous dispersion.
Chemical-aqueous	Reduction at lower and room temperature.	Agglomeration of rGO sheets in the aqueous dispersion/ no distinct lamellar structure for the produced membranes.
Chemical-vapor	Flexible and well-ordered layered prepared membranes/ high quality reduction method.	Applicable for limited reducing agent.

4. Challenges and future outlook

GO and rGO membrane filtration processes offer several benefits including flexibility of operation, good mechanical stability, and good removal capability. However, like every other technology, there are some drawbacks that need to be overcome. First, relatively low rejection ability and mechanical stability of GO and rGO membranes for selective separation have limited their use in practical applications that require long-term performance stability. Second, although the dissolution of Al^{3+} is an effective way to produce a competent membrane for water filtration, the need for the AAO filter discs currently places size constraints on membranes. The reason is due to the size of commercially available filter media. Further, the AAO filter discs are relatively expensive and fragile. Finally, the thickness of membrane significantly regulates the membrane separation performances and controlling the thickness of the membrane is a great challenge. Therefore, GO and rGO membranes need additional improvements before commercialization for filtration applications. One of the solutions to overcome these challenges is composite membranes.

5. Composite membranes

One of the solutions to overcome the above drawbacks is to produce composite membranes. The type of polymer used for composite membrane preparation and filtration applications is important because it determines permeate quality and operating cost of membrane production. Recently developed GO nanosheets and their composite membranes have enhanced stability and more possibilities for practical applications. Adding an extremely low amount of graphene-based nanoplatelets into a polymer matrix can significantly improve not only mechanical stability but also hydrophilicity and overall separation performances. Because the amount of graphene-based materials added to the polymer matrix is less, the process of producing composite membranes will be cost effective as well.

In general, composite membranes are a modified type of polymeric membranes with nanomaterials dispersed in their matrices. These membranes are prepared by introducing nanoparticle materials as fillers into macroscopic sample materials as matrix. These composite membranes fabricated with fillers enhance electrical, thermal, and mechanical properties of the polymeric membranes. Nanoparticle materials (nanofillers) used in the composite membranes are classified as below and their advantages and disadvantages are defined in **Table 3**. This table shows a brief comparison between different types of nanofillers.

- Carbonaceous materials
- Inorganic materials (metals, ceramics, and metallic oxides)
- Biomaterials

It is worth to point out inorganic nanofillers in composite membranes preparation are found to enhance permeate flux, rejection capability, and to improve thermal, chemical, and mechanical stabilities. However, because the size of metal and metal oxide nanofillers is in micrometer range, their applications are limited to microfiltration and ultrafiltration areas. Graphene-based materials due to high surface area and strong mechanical stability, they have shown great importance in practical filtrations applications with longer separation performances. For example, GO added to a polymer matrix due to lamellar ionic nanochannels and higher hydrophilicity, and the ability for functionalization, it has a great interest in nanofiltration applications.

Table 3. A comparison between different types of nanofillers in the composite membranes.

Nanofiller	Example	Properties in the composite membranes
Nanoparticles	SiO ₂ , TiO ₂ , MgO, Al ₂ O ₃	The loading of nanoparticles is high (2-30%), agglomeration issue, generation of larger interfacial voids, having an adverse effect on mechanical stability due to the agglomeration, applicable for specific filtration applications.
1D dimensional nanofiller	Carbon nanotube, nanorods, nanofibers	Due to its hydrophobicity, carbon nano tubes are non-soluble in most solvents and water, poor compatibility with polymers, aggregation issue, Possibility of functionalization. Maximum loading of functionalized carbon nanotube is 5% based on literature.
2D dimensional nanofiller	GO/rGO/MoS ₂	High surface area, lower loading of nanosheets, possibility of functionalization by acidifications, having a lamellar structure to separate ions and molecules, strong mechanical strength, graphene-based composite membranes (GO-polymer composite membranes) can be regenerated by passing HCl acid (30 min) on the membrane surface, which can be reusable.